इंटरनेट मानक

Disclosure to Promote the Right To Information

Whereas the Parliament of India has set out to provide a practical regime of right to information for citizens to secure access to information under the control of public authorities, in order to promote transparency and accountability in the working of every public authority, and whereas the attached publication of the Bureau of Indian Standards is of particular interest to the public, particularly disadvantaged communities and those engaged in the pursuit of education and knowledge, the attached public safety standard is made available to promote the timely dissemination of this information in an accurate manner to the public.

"जानने का अधिकार, जीने का अधिकार"
Mazdoor Kisan Shakti Sangathan
"The Right to Information, The Right to Live"

"पुराने को छोड नये के तरफ"
Jawaharlal Nehru
"Step Out From the Old to the New"

IS 13360-2-1 (1992): Plastics - Methods of test, Part 2: Sampling and preparation of test specimens, Section 1: Compression moulding test specimens of thermoplastics materials [PCD 12: Plastics]

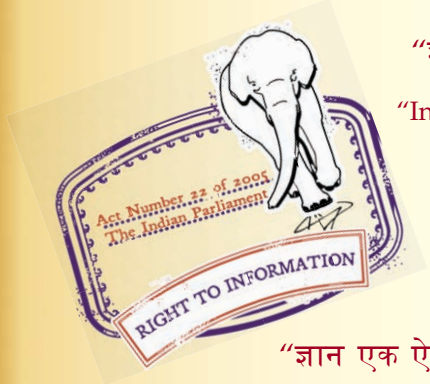

"ज्ञान से एक नये भारत का निर्माण"
Satyanarayan Gangaram Pitroda
"Invent a New India Using Knowledge"

"ज्ञान एक ऐसा खजाना है जो कभी चुराया नहीं जा सकता है"
Bhartṛhari—Nītiśatakam
"Knowledge is such a treasure which cannot be stolen"

BLANK PAGE

PROTECTED BY COPYRIGHT

IS 13360 (Part 2/Sec 1) : 1992

भारतीय मानक

(Reaffirmed 2003)

प्लास्टिक — परीक्षण की पद्धतियाँ

भाग 2 परीक्षण बानगियों के नमूने लेना और तैयार करना

अनुभाग 1 ताप प्लास्टिक सामग्री के संपीडन सँचकन परीक्षण नमूने

Indian Standard

PLASTICS — METHODS OF TEST

PART 2 SAMPLING AND PREPARATION OF TEST SPECIMENS

Section 1 Compression Moulding Test Specimens of Thermoplastic Materials

UDC 678·073 : 678·027·72 : 620·115·8

© BIS 1992

BUREAU OF INDIAN STANDARDS
MANAK BHAVAN, 9 BAHADUR SHAH ZAFAR MARG
NEW DELHI 110002

March 1992

Price Group 2

FOREWORD

This Indian Standard was adopted by the Bureau of Indian Standards, after the draft finalized by the Methods of Test for Plastics Sectional Committee had been approved by the Petroleum, Coal and Related Products Division Council.

For reproducible test results, specimens with a defined state are required. In contrast to injection moulding, the aim of compression moulding is to produce test specimens and sheets for machining or stamping of test specimens which are homogeneous and isotropic.

In the process of compression moulding, mixing of material takes place on a negligible scale. Granules and powders fuse only at their surfaces and preforms (milled sheets) are only partially softened.

Isotropic and homogeneous specimens can, therefore, only be obtained when the moulding material is itself, homogeneous and isotropic. This has to be considered when processing multiphase materials, such as ABS which retain their internal structure.

In order to obtain mouldings in a reproducible state, the main steps of the procedure including the four cooling methods are standardized. For each material the required moulding temperature and cooling methods shall be as specified in the appropriate Indian Standards for the material or as agreed to between the interested parties.

This standard has been aligned with ISO 293 : 1986 'Plastics-compression moulding test specimens of thermoplastic materials' issued by the International Organization for Standardization (ISO).

In reporting the results of a test or analysis made in accordance with this standard, if the final value, observed or calculated, is to be rounded off, it shall be done in accordance with IS 2 : 1960 'Rules for rounding off numerical values (*revised*)'.

Indian Standard

PLASTICS — METHODS OF TEST

PART 2 SAMPLING AND PREPARATION OF TEST SPECIMENS

Section 1 Compression Moulding Test Specimens of Thermoplastic Materials

1 SCOPE

This Standard describes the general principles and the procedures to be followed with thermoplastics in the preparation of compression-moulded test specimens and sheets from which test specimens may be machined or stamped.

NOTE — The procedure is not recommended for reinforced thermoplastics.

2 REFERENCES

The following Indian Standards are necessary adjuncts to this standard:

IS No.	*Title*
919 (Part 1) : 1963	Recommendations for limits and fits for engineering : Part 1 General engineering
2267 : 1972	Polystyrene moulding materials (*first revision*)
2828 : 1964	Glossary of terms used in the plastic industry
3073 : 1967	Assessment of surface roughness
8543 (Part 3 Sec 1) : 1978	Methods of testing plastics: Part 3 Preparation of test specimens, Secion 1 Compression moulded test specimens
9766 : 1992	Flexible PVC compounds

3 DEFINITIONS

3.1 For the purpose of this standard the definitions given in IS 2828 : 1964 and the following shall apply.

3.2 Moulding Temperature

The temperature of the mould or the press platens during the preheating and moulding time, measured in the nearest vicinity to the moulded material.

3.3 Demoulding Temperature

The temperature of the mould or the press platens at the end of the cooling time, measured in the nearest vicinity to the moulded material.

NOTE — For positive moulds, holes are normally drilled in the mould for measuring the temperatures defined in 3.2 and 3.3.

3.4 Preheating Time

The time required to heat the material in the mould up to the moulding temperature while maintaining the contact pressure.

3.5 Moulding Time

The time during which full pressure is applied while maintaining the moulding temperature.

3.6 Cooling Rate

Constant rate of cooling in a defined temperature range obtained by controlling the flow of the cooling fluid in such a way that over each 10 min interval the deviation from this specified cooling rate shall not exceed the specified tolerance.

The cooling rate is usually expressed in Kelvins per hour.

3.7 Average Cooling Rate (Non-linear)

Rate of cooling by a constant flow of the cooling fluid, calculated by dividing the difference between moulding and demoulding temperatures by the time required to cool the mould to the demoulding temperature.

The average cooling rate is usually expressed in Kelvins (K) per minute.

4 APPARATUS

4.1 Moulding Press

The press shall have a clamping force capable of applying a pressure (conventionally given as the ratio of the clamping force to the area of the mould cavity) of at least 10 MPa.

The pressure shall be manintained to whithin 10 percent of the specified pressure during the moulding cycle.

The platens shall be capable of:

1) being heated to at least 240°C; and
2) being cooled at a rate given in the table (*see* **5.3.2**).

The difference between the temperatures of any points of the mould surfaces shall not vary by more than $\pm$ 2 *K* during heating and $\pm$ 4 *K* during cooling.

When the heating and cooling system is incorporated in the mould, it shall comply with the same conditions.

The platens or mould shall be heated either by high-pressure steam, or by a heat-conducting fluid in an appropriate channel system, or by using electric heating elements. The platens or mould are cooled by a heat-conducting fluid (usually cold water) in a channel system.

For quench cooling (*see* Method C in the table), two presses shall be used, one for heating during moulding and the other for cooling.

NOTES

1 For a specified cooling method, the flow rate of the heat-conducting fluid should be predetermined in a test without any material in the mould.

2 The temperature may be constantly controlled in the centre between each upper and lower platen of the press.

4.2 Moulds

4.2.1 *General*

The characteristics of the test specimens prepared by using different types of mould are not the same. In particular, the mechanical properties depend on the pressure applied to the material during cooling.

In general, two types of mould, "flash moulds" (*see* Fig. 1) and "positive moulds (*see* Fig. 2) are used for compression moulding test specimens of thermoplastics.

Flash moulds permit excess moulding material to be squeezed out and do not exert moulding pressure on the moulding material during cooling. They are particularly convenient for preparing test specimens or panels of similar thickness or comparable levels of low internal stress.

With positive moulds, the full moulding pressure, neglecting friction, is exerted on the material during cooling. The thickness, stress and density of the resulting mouldings depend on mould construction, size of material charge and the moulding and cooling conditions. This type of mould produces consolidated test specimens with moulded surfaces and is therefore, particularly suitable for obtaining flat surfaces or suppressing the formation of voids within test specimens.

4.2.2 *Fabrication*

The moulds shall be made of materials capable of withstanding the moulding temperature and pressure. The surfaces in contact with the material shall be polished to obtain a good surface condition on the specimens (recommended surface roughness 0·16 *Ra* (*see* IS 3073 : 1967). Specimen removal can be made easier by chromium plating these surfaces. For specimens of small dimensions a 2° taper is strongly recommended.

Blind holes may be drilled in the mould so that temperature can be measured in the vicinity of the moulded material by using thermocouples or mercury thermometers.

NOTES

1 Depending on the performance of the press (*see* **4.1**) the moulds may have built-in heating and/or cooling devices similar to those described for the press platens.

2 An alloy steel, resistant to mechanical shock and heat treated to provide a tensile strength of 2 200 MPa, will generally be satisfactory for the moulds. However, in the special case of PVC moulding materials, the use of martensite stainless steel treated to provide a tensile strength of 1 050 MPa is recommended.

4.2.3 *Types*

The types of the mould used shall be capable of producing test specimens of the types and states specified in the appropriate Indian Standards for the materials or shall be agreed to upon between the interested parties.

FIG. 1 TYPE OF FLASH (PICTURE FRAME) MOULDS

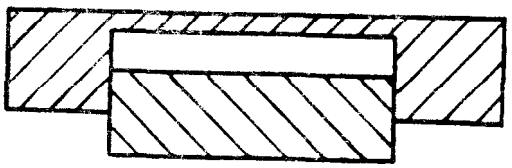

FIG. 2 POSITIVE-TYPE MOULD

4.2.3.1 *Flash (picture frame) moulds*

With this type of mould, the excess material is squeezed out and the moulding pressure during cooling is only exerted on the frame and not on the materials. The thickness in the centre of the mouldings is slightly less than at the edges due to the shrinkage during cooling. Directly moulded test bars may also have sink markes or voids if the shrinkage is hindered by sticking of the plastic material to the mould.

To overcome these disadvantages, stamping or machining of test specimens from the central part of compression moulded sheets is preferred.

For moulding sheets, simple and economical flash moulds can be used, consisting of a frame covered with two plates (*see* Fig. 1). The lower and upper plates, having a thickness of about 1 to 2 mm can be made from polished steel or chromium-plated brass to aid release. To avoid the plastic material sticking to the plates, they can be covered by a flexible foil, for example, aluminium or polyester.

Use of a release agent is not allowed.

The thickness of the chase shall be appropriate to the moulded sheet thickness.

The size of the moulding frame shall be appropriate to the moulded sheet thickness.

The size of the moulding frame shall be such that specimens can be cut or machined without using the outer 20 mm perimeter of the sheet.

4.2.3.2 *Positive moulds*

Theee moulds (*see* Fig. 2) are fitted with one or two male pistons and a female part. They allow known pressure, neglecting friction, to be applied to the material, and to be maintained during the moulding and cooling times.

The thickness of the moulding will depend on the quantity of material, its thermal expansion and the loss of material due to clearances in the moulds. The losses will be a function of the flow of the material at the chosen moulding temperature, the applied pressure, the time over which the pressure is applied, mould construction, etc.

Correct guidance of the male part in the female part is facilitated by use of a round cavity. A fit between these parts of H7g6 [*see* IS 919 (Part 1) : 1963] is recommended, that is between 15 μm and 90 μm for a round cavity of diameter 200 mm. The mould may be fitted with one or several ejection pins to make part removal easier.

Shims may be used in positive moulds to aid in controlling thickness. These are removed at the start of the cooling phase.

5 PROCEDURE

5.1 Preparation of Moulding Material

5.1.1 *Drying of Granular Material*

Dry the granular material as specified in the relevant Indian Standard or in accordance with the material supplier's instructions. If no instructions are given, dry for 24 $\pm$ 1 h at 70 $\pm$ 2°C in an oven.

5.1.2 *Preparation of Preforms*

Direct moulding of sheet from granules shall be the standard procedure, provided that a sufficiently homogeneous sheet is obtained. Normally this means that the sheet is free from surface irregularities and internal imperfections. Direct moulding from powder or granules may sometimes require melt homogenization using a hot melt milling or mixing procedure to achieve a satisfactory final sheet. Conditions shall be used that do not degrade the polymer. This can usually be achieved by not milling or mixing for more than 5 min after melting. The preform sheet obtained shall be thicker than the test sheet to be moulded and of sufficient size to enable the test sheet to be moulded.

NOTE — Storing the preforms in a dry, airtight container is recommended.

5.2 Moulding

5.2.1 Adjust the mould temperature to within $\pm$ 5 *K* of the moulding temperature specified in the relevant Indian Standard or as agreed to between the interested parties.

Place a weighed quantity of material (granules or preforms) in the preheated mould. If granular material is used, make sure that it is evenly spread over the mould surface. The mass of the material shall be sufficient to fill the cavity volume when it is melted and allow about a 10 percent loss for a flash mould and about a 3 percent loss for a positive mould;

With flash moulds, cover the mould with flexible foils (*see* **4.2.3.1**) and then place the mould in the preheated press.

Close the press and preheat the material charge by applying a contact pressure for 5 min. Then apply full pressure for 2 min (moulding time, *see* **3.5**) and then cool down (*see* **5.3**).

NOTES

1 A preheating time of 5 min is the standardized time for evenly spread material charges sufficient for sheets up to 2 mm thickness. For thicker mouldings, this time has to be adjusted accordingly.

2 At contact pressure, the press is just closed with a pressure low enough to avoid flow of the material. Full pressure means a pressure sufficient to shape the material and squeeze out the excess material.

5.3 Cooling

5.3.1 *General*

With some thermoplastics, the cooling rate affects the ultimate physical properties. For this reason, the cooling methods are specified in the table.

The method of cooling shall always be stated together with the final physical properties. The appropriate cooling method is normally given in the relevent Indian Standard for the material. If no method is indicated, Method B shall be used.

5.3.2 *Cooling Methods*

The appropriate cooling method shall be selected from the table.

In the case of quench cooling (*see* Method C in the table), transfer the mould assembly from the heating press to the cooling press as quickly as possible by suitable means, for examaple, using a pair of tongs.

Table 1 Cooling Methods

Cooling Method	Average Cooling Rate (*see* 3.7) K. Min $^{-1}$	Cooling Rate (*see* 3.6) K. h $^{-1}$	Remarks
A	10 ± 5	—	—
B	15 ± 5	—	—
C	60 ± 30	—	Quench cooling
D	—	$5 \pm 0{\cdot}5$	Slow cooling

The demoulding temperature shall be 40°C if no other instructions are given.

NOTES

1 The use of two pressure is required for Method C (*see* 4 1).

2 Method D is recommended for producing test specimens free of any internal stress or for slow cooling after annealing of previously prepared sheets.

6 INSPECTION OF THE MOULDED SPECIMENS OR SHEETS

6.1 After cooling, check the moulded specimens or sheets for appearance that is for sink marks, shrink holes, discolorations) and for conformance to specified dimensions. If any moulding defects are found, the test specimens or sheets shall be discarded.

Make sure that there is no degradation or unwanted crosslinking, using the method specified in the relevant Indian Standard or as agreed to between the interested parties.

7 TEST REPORT

7.1 The test report shall contain the following information:

a) Reference to this Indian Stardard;

b) Dimension of the specimen and its intended use;

c) Complete identification of moulding (type, designation, etc);

d) Preparation of moulding material:

   1) drying conditions for granulates and powder

   2) processing and conditions used in the preparation of preforms and their average thickness;

e) Type of mould and foil used;

f) Moulding conditions:

   1) preheating time

   2) moulding temperature, pressure and time

   3) cooling method used

   4) demoulding temperature;

g) State of specimen, if applicable; and

h) Any other observations.

Standard Mark

The use of the Standard Mark is governed by the provisions of the *Bureau of Indian Standards Act, 1986* and the Rules and Regulations made thereunder. The Standard Mark on products covered by an Indian Standard conveys the assurance that they have been produced to comply with the requirements of that standard under a well defined system of inspection, testing and quality control which is devised and supervised by BIS and operated by the producer. Standard marked products are also continuously checked by BIS for conformity to that standard as a further safeguard. Details of conditions under which a licence for the use of the Standard Mark may be granted to manufacturers or producers may be obtained from the Bureau of Indian Standards.

Bureau of Indian Standard

BIS is a statutory institution established under the *Bureau of Indian Standards Act, 1986* to promote harmonious development of the activities of standardization, marking and quality certification of goods and attending to connected matters in the country.

Copyright

BIS has the copyright of all its publications. No part of these publications may be reproduced in any form without the prior permission in writing of BIS. This does not preclude the free use, in the course of implementing the standard, of necessary details, such as symbols and sizes, type or grade designations. Enquiries relating to copyright be addressed to the Director (Publications), BIS.

Revision of Indian Standards

Indian Standards are reviewed periodically and revised, when necessary and amendments, if any, are issued from time to time. Users of Indian Standards should ascertain that they are in possession of the latest amendments or edition. Comments on this Indian Standard may be sent to BIS giving the following reference:

Doc : No. PCD 23 (1031)

Amendments Issued Since Publication

Amend No.	Date of Issue	Text Affected

BUREAU OF INDIAN STANDARDS

Headquarters :

Manak Bhavan, 9 Bahadur Shah Zafar Marg, New Delhi 110002
Telephones : 331 01 31, 331 13 75

Telegrams : Manaksanstha
(Common to all Offices)

Regional Offices :	Telephone
Central : Manak Bhavan, 9 Bahadur Shah Zafar Marg NEW DELHI 110002	{331 01 31 {331 13 75
Eastern : 1/14 C. I. T. Scheme VII M, V. I. P. Road, Maniktola CALCUTTA 700054	37 86 62
Northern : SCO 445-446, Sector 35-C, CHANDIGARH 160036	53 38 43
Southern : C. I. T. Campus, IV Cross Road, MADRAS 600113	235 02 16
Western : Manakalaya, E9 MIDC, Marol, Andheri (East) BOMBAY 400093	6 32 92 95

Branches : AHMADABAD, BANGALORE, BHOPAL, BHUBANESHWAR, COIMBATORE, FARIDABAD, GHAZIABAD, GUWAHATI, HYDERABAD, JAIPUR, KANPUR, LUCKNOW, PATNA, THIRUVANANTHAPURAM.

Printed at Printwell Printers, Aligarh, India